

Design of experiments to study the risk of sous vide cooking for possible migration of hazardous compounds from the packaging to the food. Analysis by DI-SPME-GC-MS and UPLC-IMS-QTOF.

Carlos Jiménez¹, Robert Paiva^{1,2}, Carolina Borja¹, Cristina Nerín¹ and Celia Domeño¹

¹ Afiliation: Grupo Universitario de Investigación Analítica (GUIA)
Institute of Engineering Research (I3A)

University of Zaragoza, Torres Quevedo Building, Campus Rio Ebro, 50018 Zaragoza, Spain.

Tel. +34-976762707, e-mail: cjimenez@unizar.es

²Afiliation: Chemistry Department, Cente for Exact Sciences,
Federal University of São Carlos (UFSCar), São Carlos, Brazil

Abstract

Using design of experiments (DoE) and response surface methodology, the influence of Sous Vide cooking time and temperature conditions on the migration of volatile and non-volatile hazardous compounds into the food was studied. Migration has been studied in HDPE-PA and PP-PA and in three simulants, analysing the compounds of interest by DI-SPME-GC-MS and UPLC-IMS-QTOF.

Introduction

Sous Vide cooking is a fashionable technique in today's gastronomy, widely used by top chefs in some of the world's best restaurants for industrial food processing and can be adapted to home cooking (Baldwin 2012). However, since the cooking technique involves the use of plastic material intended to come into direct contact with the food, it is necessary to consider not only the preservation of the organoleptic and nutritional properties of the food, but also the risk of possible hazardous compounds that may migrate from the packaging to the food (Vera et al. 2023; Su et al. 2021; Cherif Lahimer et al. 2017; Arvanitoyannis, Bosnea 2004).

Regulation (EC) No 1935/2004 of the European Parliament and of the Council makes it clear that the basic rules apply to all food contact materials. One of the main criteria is that this material must be sufficiently inert so as not to transfer, through migration processes, high-risk substances that could affect the health of the consumer and/or alter organoleptic properties.

Novel techniques such as DI-SPME-GC-MS and UPLC-IMS-QTOF have been used to identify the compounds. For the migration tests, three simulants have been used under the conditions of the legislation.

Aims

The objective is to study the influence of sous vide cooking conditions, temperature and time on the risk of migration of volatile and non-volatile substances from the packaging to the food.

Method

The methodology of the migration study, as well as the analyses carried out, are presented in the form of a flow chart in Figure 1. The experimental conditions carried out, including the variables of the factorial design (v1 and v2), are presented in Table 1.

Results

In this study, different volatile and semi volatile compounds, including IAS and NIAS, have been identified in two plastic bags (i) bioriented polyamide and polypropylene (PP + PA) and (ii) bioriented polyamide and high-density polyethylene (HDPE + PA). Compounds of interest have been found in all simulants.

As the example in Figure 2 shows, temperature (v2) has a higher effect than time (v1) or the interaction between time and temperature (v12). Table 2 shows the list of the volatile and non-volatile compounds identified.

Conclusions

Temperature has been shown to be the key factor in the number of compounds migrating to 10% ethanol in PP+PA plastic bags, as suggested in figure 3. In fact, the maximum migration conditions start after 250 minutes and with the temperature above 68°C.

A part of the compounds is intentionally added substances (IAS) and used as plasticisers (phthalates and adipates), antioxidants (2,4-Di-tert-butylphenol)

and additives to improve the mechanical properties of the plastic (13-Docosamide, (Z)-; Diphenyl sulfone).

The rest of the compounds found are non-intentionally added substances (NIAS) which may originate from side reactions, contamination (p-xylene) or decomposition products (7,9-Di-tert-butyl-1-oxaspiro(4,5)deca-6,9-diene-2,8-dione: degradation product of antioxidants).

Quantification of these compounds should be carried out to fully assess the risk to human health.

REFERENCIAS

- [1]. ARVANITTOYANNIS, Ioannis S. and BOSNEA, Loulouda, 2004. Migration of Substances from Food Packaging Materials to Foods. *Critical Reviews in Food Science and Nutrition*. 2004. Vol. 44, no. 2, pp. 63–76. DOI 10.1080/10408690490424621.
- [2]. BALDWIN, Douglas E., 2012. Sous vide cooking: A review. *International Journal of Gastronomy and Food Science*. 1 January 2012. Vol. 1, no. 1, pp. 15–30. DOI 10.1016/j.ijgfs.2011.11.002.
- [3]. CHERIF LAHIMER, Meriem, AYED, Naceur, HORRICHE, Jalel and BELGAIED, Sayda, 2017. Characterization of plastic packaging additives: Food contact, stability and toxicity. *Arabian Journal of Chemistry*. 1 May 2017. Vol. 10, pp. S1938–S1954. DOI 10.1016/j.arabjc.2013.07.022.
- [4]. REGULATION (EC) NO 1935/2004, 2004. Regulation (EC) No 1935/2004 of the European Parliament and of the Council of 27 October 2004 on materials and articles intended to come into contact with food and repealing Directives 80/590/EEC and 89/109/EEC. . 2004.
- [5]. SU, Qi Zhi, VERA, Paula, SALAFRANCA, Jesús and NERÍN, Cristina, 2021. Decontamination efficiencies of post-consumer high-density polyethylene milk bottles and prioritization of high concern volatile migrants. *Resources, Conservation and Recycling*. 1 August 2021. Vol. 171. DOI 10.1016/j.resconrec.2021.105640.
- [6]. VERA, Paula, CANELLAS, Elena, SU, Qi Zhi, MERCADO, Daniel and NERÍN, Cristina, 2023. Migration of volatile substances from recycled high density polyethylene to milk products. *Food Packaging and Shelf Life*. 1 March 2023. Vol. 35. DOI 10.1016/j.fpsl.2022.101020.

Table 1. Experimental conditions and factorial planning variables in the migration study using DoE.

Experiment Nomenclature	Time (v1)		Temperature (v2)	
	min	Norm.	°C	Norm.
E1	15	-1	50	-1
E2	15	-1	80	1
E3	247,5	0	65	0
E4	480	1	50	-1
E5	480	1	80	1

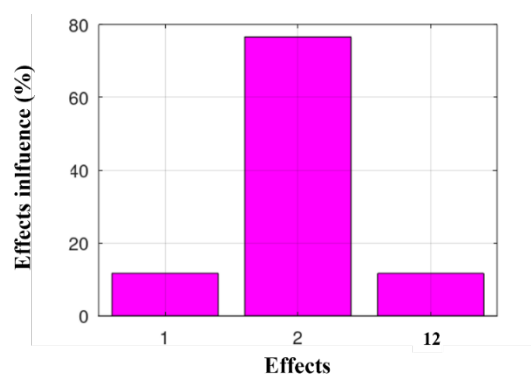


Figure 2. Variable effect diagram (1: time, 2: temperature and 12: interaction 1-2) for PP+PA bags

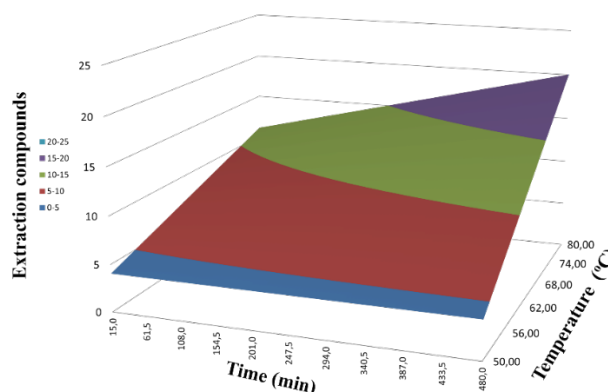


Figure 3. Surface response for PP + PA bags in ethanol 10%

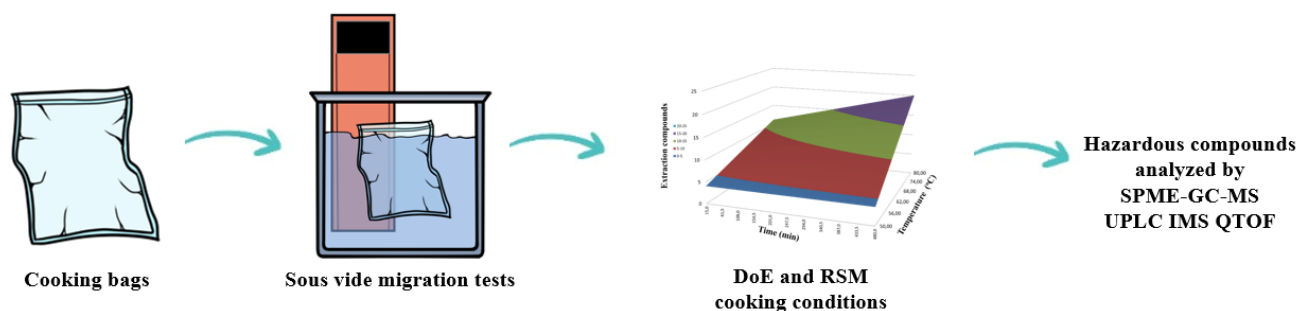


Figure 1. Methodology flowchart

Table 3. Volatile and semi-volatile compounds identified for PP bags in ethanol 10% by SPME-GC-MS

RT (min)	Compound	CAS	Formula	Classification
6.33	p-Xylene	106-42-3	C ₈ H ₁₀	NIAS
6.79	Styrene	100-42-5	C ₈ H ₈	NIAS
7.48	Oxime-, methoxy-phenyl_	1000222-86-6	C ₈ H ₉ NO ₂	NIAS
16.35	2,4-Di-tert-butylphenol	96-76-4	C ₁₄ H ₂₂ O	Antioxidant/ UV
17.37	Diethyl Phthalate	84-66-2	C ₁₂ H ₁₄ O ₄	Plasticizer
17.80	p-Octylacetophenone	10541-56-7	C ₁₆ H ₂₄ O	NIAS
19.35	3,5-di-tert-Butyl-4-hydroxybenzaldehyde	1620-98-0	C ₁₅ H ₂₂ O ₂	NIAS
20.37	Phthalic acid, isobutyl octyl ester	1010309-04-5	C ₂₀ H ₃₀ O ₄	Plasticizer
20.41	2,5-di-tert-Butyl-1,4-benzoquinone	2460-77-7	C ₁₄ H ₂₀ O ₂	NIAS
20.91	7,9-Di-tert-butyl-1-oxaspiro(4,5)deca-6,9-diene-2,8-dione	82304-66-3	C ₁₇ H ₂₄ O ₃	Antioxidant (NIAS)
21.03	Diphenyl sulphone	127-63-9	C ₁₂ H ₁₀ O ₂ S	Thermosetting
21.11	Benzenepropanoic acid, 3,5-bis(1,1-dimethylethyl)-4-hydroxy-, methyl ester	6386-38-5	C ₁₈ H ₂₈ O ₃	Antioxidant
21.21	n-Hexadecanoic acid	57-10-3	C ₁₆ H ₃₂ O ₂	NIAS
21.30	Dibutyl phthalate	84-74-2	C ₁₆ H ₂₂ O ₄	Plasticizer
21.60	3,5-di-tert-Butyl-4-hydroxyphenylpropionic acid	20170-32-5	C ₁₇ H ₂₆ O ₃	Additive (Fenozan)
21.89	9-Acetylphenanthrene	2039-77-2	C ₁₆ H ₁₂ O	NIAS
23.09	Octadecanoic acid	057-11-4	C ₁₈ H ₃₆ O ₂	Additive
23.29	9-Octadecenamide, (Z)	301-02-0	C ₁₈ H ₃₅ NO	Additive (Resistance)
25.13	Diisooctyl adipate	1330-86-5	C ₂₂ H ₄₂ O ₄	Plasticizer
26.02	Hexadecanoic acid, 2-hydroxy-1-(hydroxymethyl)ethyl ester	23470-00-0	C ₁₉ H ₃₈ O ₄	NIAS
27.61	Octadecanoic acid, 2,3-dihydroxypropyl ester	123-94-4	C ₂₁ H ₄₂ O ₄	Additive
28.04	13-Docosenamide, (Z)-	112-84-5	C ₂₂ H ₄₃ NO	Slip additive