# Enhanced methanation assisted by CO<sub>2</sub> adsorption on a bimetallic catalytic fixed bed reactor

V. D. Mercader\*, P. Sanz-Monreal, P. Durán, P. Aragüés-Aldea, E. Francés, J. Á.

Peña, J. Herguido

Grupo de Catálisis e Ingeniería de Reactores (CREG) Instituto de Investigación en Ingeniería de Aragón (I3A) Universidad de Zaragoza, Mariano Esquillor s/n, 50018, Zaragoza, Spain. Tel. +34-976762707, e-mail: <u>vmercader@unizar.es</u>

#### Abstract

This work studies the influence of introducing a CO<sub>2</sub> adsorbent in a bimetallic catalytic fixed bed reactor. The catalyst is a lab-made Fe-Ni alloy (2.5:7.5%  $^{wt}/_{wt}$ ) supported on gamma alumina. Two CO<sub>2</sub> adsorbents were tested in this study, a lab made CaO and a Na<sub>2</sub>O (10%  $^{wt}/_{wt}$ ) supported on gamma alumina.

#### Introduction

During the last years CO<sub>2</sub> emissions achieved critical levels generating important environmental damages. If the carbon dioxide generation is not dramatically reduced, a hypothetic Point of No Return might arrive in an early future. Even though the need to reduce emissions is critical, some inevitable economical activities will continue producing CO<sub>2</sub>. In addition, the energy supply is highly dependent on fossil fuels. In this line, hydrogen has been studied as an alternative energy vector, which could be produced with surplus electricity from renewables. However, hydrogen uses are still limited by its challenging store and transport. In order to solve the environmental problem and the hydrogen storage limitations, a set of new technologies have been proposed labelled as Power to Gas (PtG). PtG uses surplus electricity from renewables to generate green hydrogen from water electrolysis. That green hydrogen is combined with a concentrated CO<sub>2</sub> flow (e.g. biogas  $-30\%^{v}$  CO<sub>2</sub> and  $70\%^{v}$  CH<sub>4</sub>- through Sabatier reaction (r.1), generating a stream enriched in CH4. Also, the resulting stream (i.e., Synthetic Natural Gas, SNG or even upgraded biogas) could be injected directly to the preexisting natural gas network [1].

$$\mathrm{CO}_2 + 4\mathrm{H}_2 \rightleftharpoons \mathrm{CH}_4 + 2\mathrm{H}_2\mathrm{O} \tag{r.1}$$

The inclusion of an alkali or an alkaline-earth group species in the catalytic bed could improve the  $CO_2$  affinity of the catalyst, creating chemical bonds between the basic groups and  $CO_2$  [2]. As result, the interaction between the fixed  $CO_2$  with H<sub>2</sub> could be

improved. Thus, the selectivity and conversion to methane might increase. In order to study the previously mentioned assumptions, two CO<sub>2</sub> adsorbents were synthesized including an alkali or alkaline earth supported on gamma alumina. Resulting adsorbents have a 10 <sup>wto</sup>% Na or 10 <sup>wto</sup>% Ca and were labelled as "Na<sub>2</sub>O" and "CaO". Benefits of blending Fe with Ni in methanation catalysts were showed in previous CREG studies [3]. The goal of this study is to experimentally assess and quantify the effects of Sorption Enhanced Sabatier Reaction - *SESaR*- intensification in a fixed-bed reactor.

### Experimental

Firstly the effect of diffusional constraints (internal and external) was studied, fixing a volumetric flow of 150 mL(STP)/min, enough to ensure kinetic regime. Experiments were carried out in a fixed bed reactor of approximately 12 cm length and 13 mm inner diameter, at atmospheric pressure. For the reaction experiments the mass of solids introduced in the column (pre-mixed) was 2 g of catalyst, 2g of CO<sub>2</sub> adsorbent (Na<sub>2</sub>O or CaO) and 6.25g of  $\gamma$ -Al<sub>2</sub>O<sub>3</sub>. Before starting a methanation experiment, the catalyst was activated at 500 °C for 2 h with a gas flow composition of 50% H<sub>2</sub>, 45% Ar and 5% N<sub>2</sub> (by vol.). After the activation stage, the temperature was decreased to the experimental conditions. These were performed at 400 °C. That temperature is adequate for the methanation reaction and this catalyst. Each methanation experiment (Table 1) includes three steps: first the reactor is fed with CO<sub>2</sub> diluted in inert (adsorption step); after that, CO<sub>2</sub> is exchanged in the inlet by H<sub>2</sub> (hydrogenation) and finally only inert gases are introduced as purge step. The concentration in the reactor outlet was measured with a micro chromatograph (Agilent 490) assisted by a continuous FTIR gas analyzer (Servomex series 4000).

## **Results and Conclusions**

Revista "Jornada de Jóvenes Investigadores del I3A", vol. 11 (Actas de la XII Jornada de Jóvenes Investigadores del I3A – 15 de junio de 2023). ISSN 2341-4790.

Reproducibility in the concentration measured at the outlet of the fixed bed reactor is presented in Figure 1. As it can be observed, results show a high reproducibility during the different repetitions of the experiment. In addition, "Cx" label indicates the number (and date) of the hydrogenation cycle, showing that the adsorbent and catalyst are stable along three adsorption-hydrogenation-purge steps.

On Figure 2 the intensification behavior for the hydrogenation step is presented. The inclusion of the CaO in the reactor bed improved the methane production by 40%. Meanwhile, the intensification for the Na<sub>2</sub>O elevated the methane production by 60%.

As general conclusion, both adsorbents showed their potential to enhance the methanation reaction

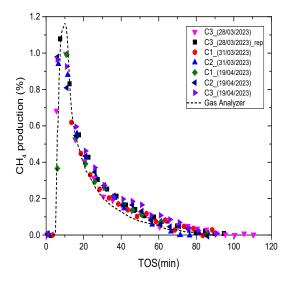


Figure 1. CH<sub>4</sub> production reproducibility of FeNi +CaO catalyst experiments carried out in the fixed bed reactor

#### Acknowledgments

This work has been carried out with financing for grant PID2019-104866RB-I00 by MCIN/AEI /10.13039/501100011033. CREG research group (T43-23R) is being supported by Gobierno de Aragón (*Aragón, SPAIN*) through *European Social Fund* (FSE-FEDER). Also, V.D.M express his gratitude for the contract PRE2020-095679, and ASM for his contract BES-2017-082069. performed by adsorption followed by hydrogenation. Thus, they will continue being studied for forward potential uses in biogas upgrading.

Table 1. Experimental conditions	
Catalyst load	2g
Adsorbent load	2g
Total volumetric flow	150 mL (STP) /
	min
CO <sub>2</sub> concentration (inlet flow)	40 °%
H <sub>2</sub> concentration (inlet flow)	5 °%
N <sub>2</sub> concentration (inlet flow)	5 °%
Inert gas (dilutant)	Ar
Pressure	1 bar
Adsorption steps duration	30 min (each one)
Methanation steps	1h and 30 min



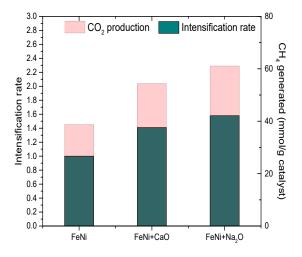


Figure 2. CH<sub>4</sub> generation and intensification rate referred to FeNi (mmol CH<sub>4</sub> generated with FeNi+adsorbent/ mmol CH<sub>4</sub> generated with only FeNi)

#### References

[1] Thema, M., Bauer, F., STerner, M. Power-to-Gas: Electrolysis and methanation status review. *Renewable and Sustainable Energy Reviews*. 112 (2019) 775–787. Available from: doi.org/10.1016/j.rser.2019.06.030.

[2] Bermejo-López, A., Pereda-Ayo, B., González-Marcos, J.A., González-Velasco, Juan R.. Alternate cycles of CO<sub>2</sub> storage and in situ hydrogenation to CH<sub>4</sub> on Ni-Na<sub>2</sub>CO<sub>3</sub>/Al<sub>2</sub>O<sub>3</sub>: influence of promoter addition and calcination temperature. *Sustainable Energy and Fuels* 5(4) (2021) 1194–1210. doi: 10.1039/d0se01677b.

[3] Sanz-Martínez, A., Durán, P., Mercader, V.D., Francés, E., Peña, J.Á., Herguido, J. Biogas Upgrading by CO<sub>2</sub> Methanation with Ni-, Ni-Fe-, and Ru-Based Catalysts. *Catal*ysis 12(12) (2022) 1609. doi: 10.3390/CATAL12121609.